



Original article

TGA/Chemometrics addressing innovative preparation strategies for functionalized carbon nanotubes



Roberta Risoluti ^a, Giuseppina Gullifa ^a, Elena Carcassi ^a, Andrea Masotti ^b,
Stefano Materazzi ^{a,*}

^a Department of Chemistry, "Sapienza", University of Rome, p.le A.Moro 5, 00185, Rome, Italy

^b Bambino Gesù Children's Hospital, IRCCS, Research Laboratories, v.le di San Paolo 15, 00146, Rome, Italy

ARTICLE INFO

Article history:

Received 5 November 2019

Received in revised form

13 February 2020

Accepted 22 February 2020

Available online 27 February 2020

Keywords:

Carbon nanotubes

Thermogravimetry

Chemometrics

Polyethyleneimine (PEI)

Polyamidoamine dendrimer (PAMAM)

ABSTRACT

In this work, functionalized carbon nanotubes (CNTs) using two polyamine polymers, polyethyleneimine (PEI) and polyamidoamine dendrimer (PAMAM), were investigated by thermal analysis in order to address preparation strategies to obtain low cytotoxic compounds with the ability to conjugate micro-RNAs and, at the same time, to transfect efficiently endothelial cells. Thermogravimetric analysis (TGA) was coupled to chemometrics as a novel analytical strategy to characterize functionalized CNTs from different preparation conditions. In particular, two starting materials were considered: very small CNTs and carboxylated CNTs (CNT-COOH) in order to examine the affinity with polymers. Chemometrics permitted to compare results from TGA and to investigate the effect of a number of factors affecting the synthesis of coated nanotubes including a different amount of involved polymer and the time required for the suspension for a satisfactory and reproducible preparation procedure. The results demonstrated the effectiveness of TGA as a tool able to address synthesis of coated CNTs to be employed as efficient drug delivery vectors in biomedical applications.

© 2020 Xi'an Jiaotong University. Production and hosting by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

1. Introduction

Carbon nanotubes (CNTs) are found to be promising materials in nanomedicine as potential drug carriers, therapeutic agents and diagnostics tools [1]. In particular, carbon nanotubes possess a good ability to cross cellular membranes because of their nanosize dimension and high surface area [2]. In addition, due to their relatively good biocompatibility, CNTs have also been employed as a novel gene delivery system in order to provide personalized medicine [3,4]. Despite their attractive features, CNTs in pristine form are not easy to manage because of the solubility [5]. Functionalization of them is often required to modify the properties of CNTs by linking radical groups into the surface with the aim of increasing their solubility in organic solvent and in water [6,7].

A number of procedures are proposed for functionalization of nanotubes according to specific applications for which they are prepared [8]. Functionalization of CNTs by oxidation, covalent and noncovalent ligand is a procedure currently used for the drug delivery in biomedical field [9–11].

In particular, due to the hydrophobic nature of CNTs, non-covalent functionalization methods are found to be suitable for amphiphilic molecules such as poly(ethylene glycol) (PEG), polyethyleneimine (PEI) or polyamidoamine dendrimer (PAMAM) which show their ability to bind siRNAs or plasmid DNA through electrostatic interactions. All these features result in coated nanoparticles with an excellent transfection efficiency [12,13]. Attempts to propose new nanomaterials able to conjugate microRNAs and to efficiently transfect endothelial cells are extensively proposed [14–18] and methods to quickly identify the effectiveness of functionalization are increasingly required.

The investigation of complex matrices is really challenging and innovative approaches aiming at processing multiparametric data are more and more attractive [19,20]. In addition, hyphenated techniques and in particular the coupling TGA/chemometrics were recently applied to real complex matrices [21,22] because of the improvement provided by the simultaneous evaluation of more than one variable. In addition, chemometrics associated with thermogravimetric data may be used not only to correlate measurements to one another but also to select the fingerprint range of the TG curves to be used to increase sensitivity and accuracy [23,24].

In this work, the coupling TGA/chemometrics is proposed as an analytical method to characterize coated CNTs to be used as drug

Peer review under responsibility of Xi'an Jiaotong University.

* Corresponding author.

E-mail address: stefano.materazzi@uniroma1.it (S. Materazzi).

delivery vectors for biomedical application. In particular, the multi-parametric approach was considered as a tool able to address the most performing conditions of functionalization leading to the most stable product.

2. Materials and methods

2.1. Samples and synthesis

Multi-walled CNTs and CNT-COOH were purchased from Cheap Tubes Inc (Cambridgeport, MA, USA), while PEI (cat no. 408727) and PAMAM generation 5 (PAMAM G = 5, cat no 536709) polymers were purchased from Sigma-Aldrich Co. (St Louis, MO, USA).

Preparation of polyamine-coated CNTs and CNTCOOH was performed using a dispersion of nanotubes (10 mg) in different solutions (2 mL) of PEI or PAMAM (40%, w/w and an exceeding quantity). In addition, the suspensions were placed in a bath sonicator for 30 min and further stirred for 24 h, 48 h and 72 h at room temperature.

2.2. Thermogravimetry

All the measurements were performed by a Perkin Elmer TGA7 Thermobalance (Massachusetts, USA). CNTs, polymers and coated nanotubes were placed into the crucible, and temperature was measured using a thermocouple directly attached to the crucible. Regardless to the method, the temperature was raised from 20 °C to 800 °C, at a heating rate of 10 °C/min, as the best resolution rate. An air flow was used as the carrier gas and maintained at a 100 mL/min flow rate. Calibration of the temperature was performed using the Curie-point transition of standard metals in order to ensure an accurate measurement of the sample temperature, as specified by the equipment recommendations. Each sample was analyzed in triplicate and a high reproducibility of the resulting curves was observed. Derivative thermogravimetric data (DTG) were also calculated to compare samples and represent the derivative of the function TG (T) with respect to T.

2.3. Chemometrics

Data were mathematically pre-treated and Principal Component Analysis (PCA) was used as the display method in order to identify

directions in the dataset with higher variability. In particular, standard normal variate transform, column autoscaling, and mean-centering [25] were considered including the first and second derivatives. Among these, the mean-centering was selected, as it provided the most performing conditions of reaction, ensuring the suitable amount of polymer in each nanotube. Diagnostics and acquisition of the thermogravimetric data were carried out by Pyris software (Thermo Fisher Scientific Inc., Waltham, MA, USA), while chemometric analysis was performed by Unscrambler X software (CAMO Analytics) to perform statistical analysis.

2.4. Experimental procedure

Thermogravimetric analysis was considered as an analytical tool able to address the synthesis of novel coated carbon nanotubes designed for the delivery of miRNAs, by evaluating the amount of polymer linked to the nanotube. To this aim, a number of variables were considered in this study, including the effect of a different amount of polymer to be linked to the nanotubes (percentage of about 40% and an exceeding amount) and the suitable time of suspension (24 h, 48 h and 72 h). In particular, the experimental design consisted of two types of nanotube (CNT and CNT-COOH) and two types of polymer (PEI and PAMAM). The selection of the different conditions of reaction was made on the basis of the research group experience in the field [26,27]. The dataset was constructed as follows: for each condition, two levels of concentration and three times of suspension were investigated in triplicate in order to ensure that the results were not batch-dependent (final dataset of 12 × 5 data). The most significant variables in samples discrimination were evaluated by the analysis of the factor loadings and a biplot (plot of the scores and loadings) was used to estimate the variables with the highest squared multiple correlation with the principal components (PCs) and factors affecting most the PCs.

3. Results and discussion

3.1. Thermogravimetric characterization

For the two kinds of CNTs and for each preparation, TGA provided the calculation of the percentage of polymer correctly adsorbed onto the nanotube. Preliminarily, the typical

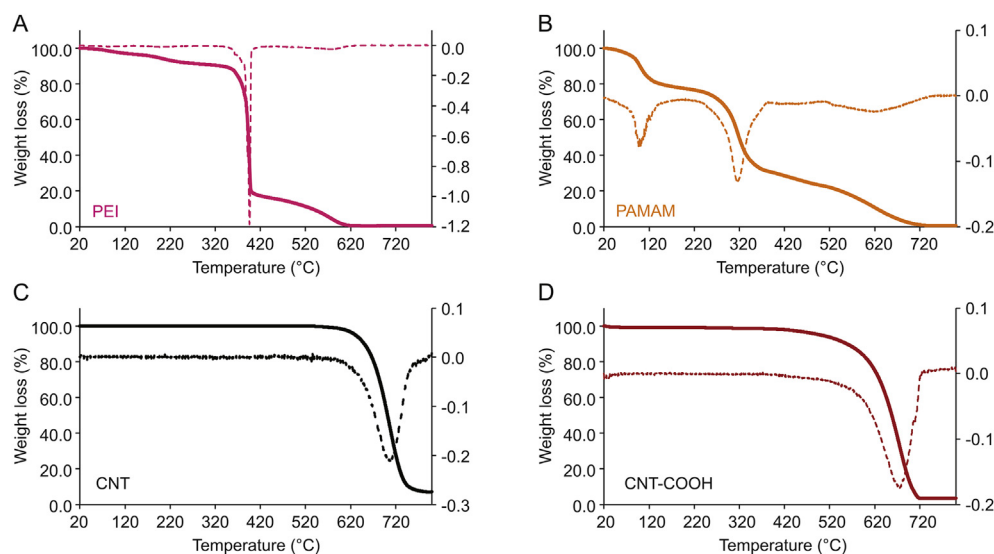


Fig. 1. TG and DTG curves of PEI (A), PAMAM (B), CNT (C) and CNT-COOH (D).

thermogravimetric behavior of the two polymers PEI (Fig. 1A) and PAMAM (Fig. 1B) as well as the two nanotubes CNT (Fig. 1C) and CNT-COOH (Fig. 1D) was defined as a result of the thermally induced decomposition in the range 20–800 °C.

Two main releasing steps may be observed in Fig. 1A for PEI corresponding to the thermally induced decomposition of the polymer respectively at 385.9 ± 0.1 °C and 462.9 ± 0.2 °C. Three main releasing steps can be described for PAMAM (Fig. 1B): the first is related to the loss of the residual solvent while the remaining two derived from the decomposition process of the polymer respectively at 312.9 ± 0.2 °C, 429.0 ± 0.6 °C and 598.6 ± 0.3 °C.

Regardless to the nanotubes, the pristine form (Fig. 1C) remains stable until 620 °C with a decomposition temperature of about 664.4 ± 0.1 °C, while for the carboxylated one (Fig. 1D) a slight decrease in the thermal stability may be observed as a consequence of the functionalization with a decomposition temperature of about 650.9 ± 0.1 °C.

For each preparation, the resulting TG and DTG curves corresponding to uncoated nanotube (blue), polymer and functionalized nanotube (green) were overlapped and reported in Fig. 2, in order to identify different decomposition processes that permit to calculate the percentage of PEI and PAMAM.

With the aim of providing the most performing procedure for coating nanotubes, three main aspects were taken into consideration: the selection of the polymer with the better affinity to the nanotube; the identification of the suitable concentration of polymer between the 40% and an exceeding amount; and the evaluation of the time required for the most performing coating procedure among 24 h, 48 h and 72 h. The calculation of the percentage of polymer adsorbed in each coated nanotube provided preliminarily interesting results, as reported in Table 1.

Despite the type of carbon nanotube involved, the PAMAM provided a significantly higher amount of adsorbed polymer (P -value of 9.31×10^{-5} and 3.24×10^{-4} respectively for CNT and CNTCOOH). This behavior may be ascribed to the interaction between the hydrophobic part of the polyamine polymer CNTs, leading to the deposition of a layer of polymer onto CNTs.

On the basis of these results, PAMAM was selected as the suitable polymer for the following experiments and the effect of a different amount of starting material (an exceeding quantity) was

Table 1

Calculated weight losses for coated CNT and CNT-COOH with PEI and PAMAM.

CNTs	PEI (%)	PAMAM (%)	P -value
CNT	10.1 ± 1.39	21.83 ± 2.63	9.31×10^{-5}
CNT-COOH-PAMAM	8.52 ± 0.61	18.00 ± 2.36	3.24×10^{-4}
P -value	2.18×10^{-2}	1.55×10^{-2}	

The data were obtained by Student's t -test with P significant < 0.05.

Table 2

Calculated weight losses for coated CNT and CNT-COOH with PAMAM using a percentage of polymer about 40% (Formulation A) and an exceeding amount (Formulation B).

CNTs	Formulation A (%)	Formulation B (%)	P -value
CNT-PAMAM	21.83 ± 2.63	21.75 ± 2.74	3.76×10^{-1}
CNT-COOH-PAMAM	18.00 ± 2.36	22.13 ± 3.12	2.73×10^{-2}
P -value	1.55×10^{-2}	8.10×10^{-1}	

The data were obtained by Student's t -test with P significant < 0.05.

Table 3

Calculated weight losses for coated CNT and CNT-COOH with PAMAM after 24 h (Formulation C), 48 h (Formulation D) and 72 h (Formulation E) of suspension.

CNTs	Formulation C (%)	Formulation D (%)	Formulation E (%)
CNT-PAMAM	23.54 ± 1.21	21.64 ± 1.08	20.94 ± 1.07
CNT-COOH-PAMAM	19.97 ± 1.79	21.08 ± 3.39	22.15 ± 3.2
P -value	7.59×10^{-4}	6.42×10^{-1}	3.24×10^{-1}

The data were obtained by Student's t -test with P significant < 0.05.

evaluated with respect to the percentage of about 40%. Results are reported in Table 2: as the quantity of starting polymer increases, only slight significant differences may be observed when functionalized CNTs are involved (P -value of 2.73×10^{-2}) while no statistically significant differences are discovered in CNTs-based formulations (P -value of 3.76×10^{-1}). As a consequence, no significant improvement was obtained when a higher amount of polymer was involved, thus suggesting considering the formulation A as the suitable condition for coating processes.

The last investigated issue was related to the optimization of the time of preparation. To this aim, further experiments were planned

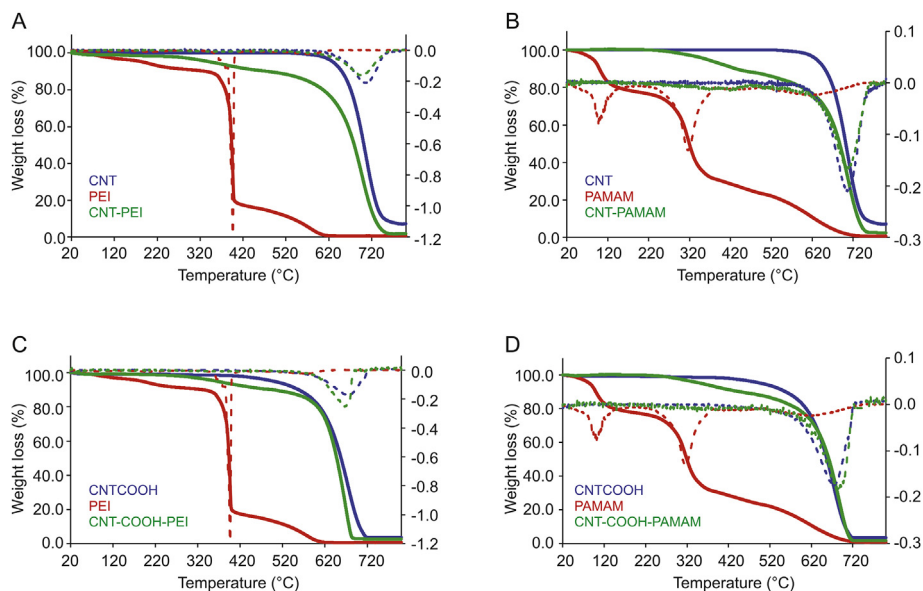


Fig. 2. Overlapped TG and DTG curves of CNT with PEI (A), CNT with PAMAM (B), CNT-COOH with PEI (C) and CNT-COOH with PAMAM (D).

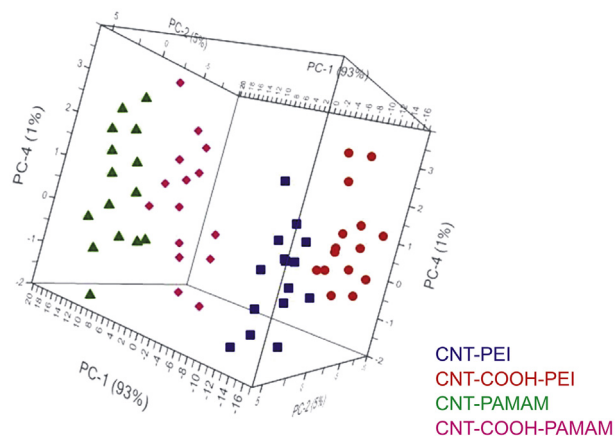


Fig. 3. 3D-scores plot of samples by principal component analysis (PCA).

for both CNT and CNT-COOH considering a time of suspension ranging from 24 h to 72 h. Results are reported in Table 3, where a significantly higher amount of adsorbed polymer was observed for pristine CNT after 24 h (P -value of 3.76×10^{-3} and 4.46×10^{-4} with respect to 48 h and 72 h, respectively) while results observed for CNT-COOH were not statistically different (P -value of 4.94×10^{-1} and 1.37×10^{-1} with respect to 48 h and 72 h, respectively). As a consequence, the increase in the time of reaction seemed to be not affecting the final amount of PAMAM recovered.

3.2. Multiparametric approach by chemometrics

All the collected data were processed by chemometrics in order to correlate results and to provide a simultaneous evaluation of the investigated variables in a single statistical analysis, and be able to address synthesis to the correct formulation. To this aim, PCA was considered as a simple exploratory tool [28,29] and results are summarized in the 3D-scores plot reported in Fig. 3, where symbols are used to represent the samples and colours are used for different formulations.

As shown in Fig. 3, the mean-centering chemometric filter permitted to achieve the most performing conditions of reaction, leading to a good reproducibility among measurements as samples

belonging to the same preparation (reported in different colours) were found to be well grouped. The location of the samples in the plot suggested that samples seemed to be differentiated moving along PC 1 (93% of explained variance) according to the percentage of polymer adsorbed by the nanotubes. In addition, samples resulted further grouped into two main clusters moving along PC 2 (5% of explained variance) according to the type of involved nanotube. The cumulative variance explained by the first four PCs was about 99.8%.

In order to evaluate the contribution of each variable on the location of the samples in the plot, the analysis of the factor loadings was performed and results are summarized in the biplot reported in Fig. 4, where symbols are used to represent the scores (the percentage of weight losses) and vectors are involved to locate the loadings (variables) in the plot.

The vector position is the direction with the highest squared multiple correlation with the PCs and indicates the factor affecting most the PCs. Consequently, the interpretation of the biplot provided several important information: first, samples located on the right side of the plot provided the highest value of polymer absorbed by the nanotubes while the samples located on left side of the plot showed the lowest values of weight losses, confirming that PAMAM offers a suitable affinity to nanotubes with respect to PEI. In addition, the length and the direction of the vectors in the plot suggested that the use of the 40% of polymer provided the most performing outcomes, resulting in a vector affecting most PC 1. Similarly, a time of about 24 h was found to be associated with the samples with higher values of adsorbed polymer as the related vector affected most PC1 with respect to the others. On the contrary, the use of the conditions represented by the vectors “48 h”, “72 h” and “excess” resulted in samples distributed along PC2 (5% of explained variance). As a consequence, those vectors slightly affected the samples separation as a function of the amount of polymer linked to the CNTs.

Finally, carboxylated nanotubes provided comparable results as the pristine nanotubes and a significant improvement in the ability of polymer adsorption were observed for pristine CNT with respect to CNT-COOH. All these findings were found to be in accordance with what was observed by the comparison of data by the evaluation of each formulation and demonstrated the ability and the feasibility of the chemometric investigation of TG data to provide the same outcomes in a single multivariate statistical analysis. In addition, the analysis of the factors loadings has clarified the role of

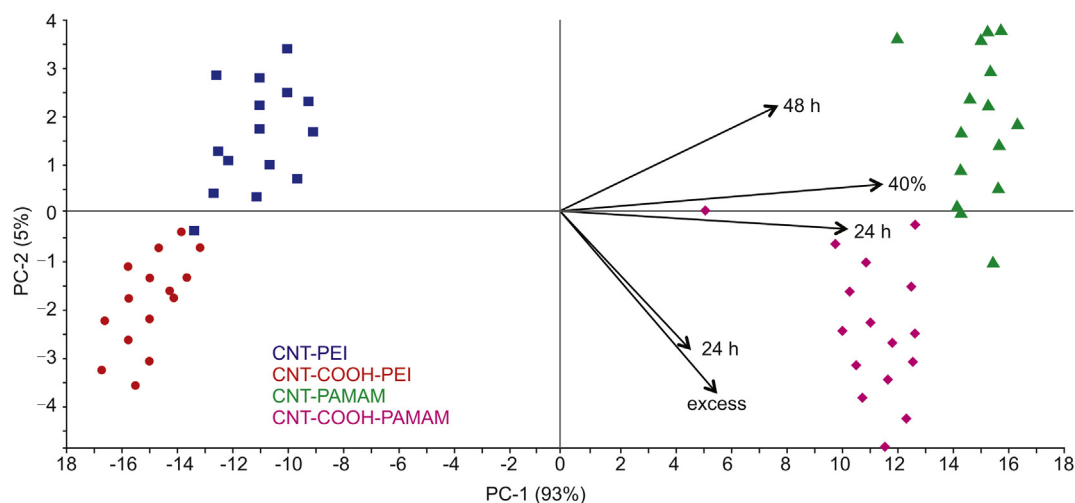


Fig. 4. Biplot of samples and loadings by principle component analysis (PCA).

each variable permitting to address preparation of polymer coated nanotubes as drug delivery vectors.

4. Conclusions

TGA was considered as an analytical tool able to identify the most performing conditions to obtain coated CNTs for biomedical applications. CNTs demonstrated to be promising materials in nanomedicine. Greater area and strength allow nanotubes to exhibit the properties of chemical and thermal stability. In this work, pristine CNT and carboxylated CNT were compared in order to propose the most performing formulation for drug delivery purposes. Among the investigated conditions, the PAMAM proved to be the suitable polymer allowing to deliver a higher amount of drug. In addition, better results were obtained when the following conditions were observed: a polymer concentration of about 40% and a time of suspension of 24 h.

The association of chemometric tools with TGA permitted a quick identification of little difference in the TG data and demonstrated the capability of estimating the suitable conditions to address the preparation of CNTs.

Conflicts of interest

The authors declare that there are no conflicts of interest.

Acknowledgments

The authors thank the Italian Ministry of Health for funding this research (Progetto Ricerca Finalizzata PE-2011-02347026).

References

- [1] B.S. Harrison, A. Atala, Carbon nanotube applications for tissue engineering, *Biomaterials* 28 (2007) 344–353.
- [2] A. Masotti, A. Caporali, Preparation of magnetic carbon nanotubes (Mag-CNTs) for biomedical and biotechnological applications, *Int. J. Mol. Sci.* 14 (2013) 24619–24642.
- [3] E.T. Thostenson, Z. Ren, T.W. Chou, Advances in the science and technology of carbon nanotubes and their composites: a review, *Compos. Sci. Technol.* 61 (2001) 1899–1912.
- [4] V. Datsyuk, K. Kalyva, K. Papagelis, et al., Chemical oxidation of multiwalled carbon nanotubes, *Carbon* 46 (2008) 833–840.
- [5] M. Prato, Controlled nanotube reactions, *Nature* 46 (2010) 172–173.
- [6] Y.L. Zeng, Y.F. Huang, J.H. Jiang, et al., Functionalization of multi-walled carbon nanotubes with poly (amidoamine) dendrimer for mediator-free glucose biosensor, *Electrochem. Commun.* 9 (2007) 185–190.
- [7] M. Catauro, E. Tranquillo, R. Risoluti, et al., Sol-Gel synthesis, spectroscopic and thermal behavior study of SiO₂/PEG composites containing different amount of chlorogenic acid, *Polymers* 10 (2018) 682.
- [8] P.E. Pehrsson, W. Zhao, J.W. Baldwin, et al., Thermal fluorination and annealing of single-wall carbon nanotubes, *J. Phys. Chem. B* 107 (2003) 5690–5695.
- [9] M.M. Barsan, M.E. Ghica, C.M. Brett, Electrochemical sensors and biosensors based on redox polymer/carbon nanotube modified electrodes: a review, *Anal. Chim. Acta* 881 (2015) 1–23.
- [10] A. Moullick, V. Milosavljevic, H.V. Nguyen, et al., Electrochemical characterization of the interaction of multiwalled carbon nanotubes with doxorubicin, *Anal. Lett.* 50 (2017) 2335–2341.
- [11] M.L. Contreras, C. Torres, I. Villarreal, et al., Molecular dynamics assessment of doxorubicin–carbon nanotubes molecular interactions for the design of drug delivery systems, *Struct. Chem.* 30 (2019) 369–384.
- [12] B. Pan, D. Cui, P. Xu, et al., Synthesis and characterization of polyamidoamine dendrimer-coated multi-walled carbon nanotubes and their application in gene delivery systems, *Nanotechnology* 20 (2009) 125101.
- [13] A. Mashat, L. Deng, A. Altawashi, et al., Zipped release from polymer-gated carbon nanotubes, *J. Mater. Chem.* 22 (2012) 11503–11508.
- [14] L. Minuti, E. Ballerini, A. Barattucci, et al., A unified strategy for the synthesis of three conical marine products, *Tetrahedron* 71 (2015) 3253–3262.
- [15] A. Asadzadeh-Firouzabadi, H.R. Zare, Preparation and application of AgNPs/SWCNTs nanohybrid as an electroactive label for sensitive detection of miRNA related to lung cancer, *Sensor. Actuator. B* 260 (2018) 824–831.
- [16] Y.T. Adem, K.A. Schwarz, E. Duenas, et al., Auristatin antibody drug conjugate physical instability and the role of drug payload, *Bioconjugate Chem.* 25 (2014) 1744–1751.
- [17] S. Materazzi, C. Foti, F. Crea, et al., Biomimetic complexes of divalent cobalt and zinc with N-heterocyclic dicarboxylic ligands, *Thermochim. Acta* 580 (2014) 7–12.
- [18] C. Papadopoulos, B. Cristóvão, W. Ferenc, et al., Thermoanalytical, magnetic and structural investigation of neutral Co(II) complexes with 2,2'-dipyridylamine and salicylaldehydes, *J. Therm. Anal. Calorim.* 123 (2016) 717–729.
- [19] A.C. Fonseca, S. Jarmelo, J. Canotilho, et al., Thermoanalytical study of N α -benzoyl-L-argininate ethyl ester chloride, *Thermochim. Acta* 527 (2012) 83–90.
- [20] R. Risoluti, M.A. Fabiano, G. Gullifa, et al., FTIR-evolved gas analysis in recent thermoanalytical investigations, *Appl. Spectr. Rev.* 52 (2017) 39–72.
- [21] S. Materazzi, J. Finamore, R. Risoluti, et al., Biomimetic complexes of Co(II), Cu(II) and Ni(II) with 2-aminomethylbenzimidazole. EGA-MS characterization of the thermally induced decomposition, *Microchem. J.* 115 (2014) 27–31.
- [22] S. Materazzi, J. Finamore, R. Risoluti, et al., Characterization of thermally induced mechanisms by mass spectrometry - evolved gas analysis (EGAMS): a study of divalent cobalt and zinc biomimetic complexes with N-heterocyclic dicarboxylic ligands, *Int. J. Mass Spectrom.* 365–366 (2014) 372–376.
- [23] S. Materazzi, R. Risoluti, G. Gullifa, et al., New frontiers in thermal analysis: a TGA/Chemometrics approach for post-mortem interval estimation in vitreous humour, *J. Therm. Anal. Calorim.* 130 (2017) 549–557.
- [24] R. Risoluti, S. Materazzi, F. Sorrentino, et al., Thermogravimetric analysis coupled with chemometrics as a powerful predictive tool for β -thalassemia screening, *Talanta* 159 (2016) 425–432.
- [25] D.L. Massart, B.G.M. Vandeginste, L.M.C. Buydens, et al., *Handbook of Chemometrics and Qualimetrics. Part B*, 20B, Elsevier, Amsterdam, 1998, pp. 88–103.
- [26] A. Paolini, G. Battafarano, V. D'oria, et al., A 3d-printed multi-chamber device allows culturing cells on buckypapers coated with pamam dendrimer and obtain innovative materials for biomedical applications, *Int. J. Nanomed.* 14 (2019) 9295–9306.
- [27] A. Celluzzi, A. Paolini, V. D'oria, et al., Biophysical and biological contributions of polyamine-coated carbon nanotubes and bidimensional buckypapers in the delivery of mirnas to human cells, *Int. J. Nanomed.* 13 (2017) 1–18.
- [28] S. Materazzi, G. Peluso, L. Ripani, et al., High-throughput prediction of AKB48 in emerging illicit products by NIR spectroscopy and chemometrics, *Microchem. J.* 134 (2017) 277–283.
- [29] R. Risoluti, A. Gregori, S. Schiavone, et al., "Click and screen" technology for the detection of explosives on human hands by a portable MicroNIR-chemometrics platform, *Anal. Chem.* 90 (2018) 4288–4292.